

Ballistic Testing Services

Report Number: BTR-12-06-2019-Sample 9

Phone: 800-513-4291 Email: [techsupport@CloseFocusResearch.com](mailto:techsupport@CloseFocusResearch.com)

CloseFocusResearch.com

Name: Midwest Glass Fabricators  
 Address: PO Box 1509, 100 Transfer Dr. Highland, MI 48357  
 Phone: Phone: 248-889-6246 / Mobile 248-249-0478

Report Date: December 6, 2019  
 Contact: Paul Mouton  
 Email: [pmouton@mwgf.com](mailto:pmouton@mwgf.com)

**Ballistic Results**

**Project Summary**  
 Type of Products to be tested: **Bullet Resistant Glazings**  
 Test Specimen Sample size(s): **12 x 12 inch**  
 Number of test specimens: **23 Samples**  
 Weight of all samples: **321.7 lbs**  
 Are Materials a Health Hazard: **No**  
 Need the Tests performed by: **within 7 to 10 days**  
 Need products shipped back: **No**  
 Purchase Order Number: **Not Applicable**


**International Ballistic Standards / Specifications Testing**  
 ASTM     Canadian     FRA     NIJ     CFR Pass All  
 Australian     EN1063     Germ DIN     State Dept     CFR SYA  
 British     EN1522/23     MIL-SAMIT     UL 752     Other  
 Test Standard: **Underwriters Laboratory UL752 (Ambient Temp. Only)**  
 Particular Test: **UL Level 2 Part 1 (.357 Magnum JSP)**  
 Velocity Range: **1,250 to 1,375 ft/s**  
 Shots: **3 shots**  
 Shot Pattern: **4.0 ± 0.5 inch triangle**

**Test Results**

Test Sample: **Sample 9**  
 Part Number / D.O.M.: **MWGF-NIJII-UL2- BR3 / November 14, 2019**    11.97 inch  
 Reference ID: **CFR NIJ II EN BR3 UL Level 2**    (304.0 mm)  
 Description: **Security Glazing**  
 Sample Size: **11.97 x 12.05 inch (304.0 x 306.1 mm)**  
 Thickness: **1.155 inch (29.34 mm)**  
 Weight: **12.65 lbs (5.74 kg)**  
 Weapon Type: **.357 Magnum**  
 Cartridge / Projectile Type: **.357 Magnum JSP**  
 Projectile Weight: **158 grains**  
 Target Distance: **15 feet**  
 Number of Shots: **3 shots**  
 Shot Sequence:

	Shot 1	Shot 2	Shot 3
Impact Velocity (ft/sec) *:	1,317	1,330	1,304
Impact Energy (ft-lbs):	608	620	596
Impact Momentum (lb-sec.):	0.92	0.93	0.91
Impact Angle (degrees):	0°	0°	0°
Sample Penetration:	NP	NP	NP
Witness Plate Penetration:	NP	NP	NP
Impact Spacing (inches) **::	4.00	4.00	4.00

Impact Spacing / Pattern: **4.00 inch (average)**  
 Witness plate material: **0.125 in. thick corrugated cardboard**  
 Spall catch box: **Not required**  
 Witness / Box Distance: **18.0 inches**  
 Spall Occurrence: **No spall occurred**  
 Test Temperature: **70 ° F**  
 Test Date: **December 06, 2019**  
 Pass / Fail Results: **Passed the Test**  
 Comments: **CFR Reference for NIJ Level II Parts 1 & 2, UL Level 2, and EN1063 BR3 (9 mm HV and .357 Magnum HV)**

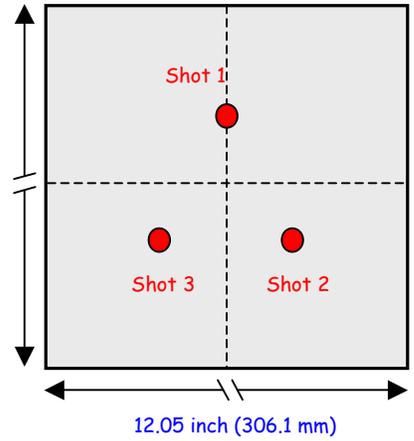

NP = No Penetration  
 PP = Partial Penetration  
 CP = Complete Penetration  
 N/A = Not Applicable

**Footnotes**

\* Velocity measurements were taken at a distance of 6 feet from muzzle.  
 \*\* Impact Spacing is the distance between shots (shot 1= 3 to 1, shot 2 = 1 to 2, shot 3 = 2 to 3)

**Test and Report Engineers**

Tested and Reported by: **Sam Raheb**

Signature: *Sam Raheb*

Date: **December 6, 2019**

Name: **Midwest Glass Fabricators**

Report Date: **December 6, 2019**

**Ballistic Test Results and Photographs**

**Ballistic Test Results:**

Test Sample 9 passed the Underwriters Laboratory UL752 UL Level 2 Part 1 (.357 Magnum JSP) Ballistic test. There was no complete penetration of the test sample from any of the .357 Magnum JSP caliber projectiles.

**Witness Plate and Spall Effects:**

No spall occurred or damage to the 0.125 in. thick corrugated cardboard witness plate was observed.

**Photographs**

The following photographs show the post-test sample. Additional larger sized photographs are included with this report.

**Sample 9: MWGF-NIJII-UL2- BR3 - D.O.M. November 14, 2019 - CFR NIJ II EN BR3 UL Level 2 - UL Level 2 Part 1 - 11.97 x 12.05 x 1.155 in.**



Sample 9 Post Test Impact Side



Sample 9 Post Test Rear Side

**Test and Report Engineers**

Tested and Reported by: **Sam Raheb**

Signature: *Sam Raheb*

Date: **December 6, 2019**